

STUDY OF MAGNETIC PROPERTIES OF MARAGING 350 STEEL AS A FUNCTION OF GRAIN SIZE *

Jônatas Targino Araújo¹
Jorge Luiz Cardoso²
Sérgio Souto Maior Tavares³
Juan Manuel Pardal⁴
Marcelo José Gomes da Silva⁵

Abstract

The magnetic properties of the maraging 350 steel were analyzed in four different grain sizes. The applications of maraging steels can be found in several fields such as aeronautics, super centrifuges, navy, etc. Thus, this kind of steel must combine excellent mechanical properties with good magnetic ones. Microstructure and grain size can affect these properties. In order to evaluate the influence of grain size in some magnetic properties such as coercive force, saturation magnetization, remanence magnetization and Magnetic Barkhausen Noise (MBN), four solution temperatures were selected to vary the grain size of the samples. The samples were also aged in two different conditions after solution annealing. Vibrating-sample magnetometer (VSM) and MBN were used to analyze the changings in the magnetic properties as the grain size increased. The results showed changing in these properties related to grain size, making it possible to choose the best heat treatment conditions for magnetic applications.

Keywords: Maraging steel; magnetic properties; grain size.

¹ *Metallurgical Engineering, undergraduation student, department of metallurgical engineering and materials, Federal University of Ceará, Fortaleza - Brazil.*

² *Eng. and Materials Science, doctor, department of metallurgical engineering and materials, Federal University of Ceará, Fortaleza – Brazil.*

³ *Eng. and Materials Science, doctor, department of mechanical engineering, Federal Fluminense University, Niteroi – Brazil*

⁴ *Mechanical Engineering, department of mechanical engineering, Federal Fluminense University, Niteroi – Brazil*

⁵ *Eng. and Materials Science, doctor, department of metallurgical engineering and materials, Federal University of Ceará, Fortaleza – Brazil.*

1 INTRODUCTION

Maraging steels have been researched over the last few years both in experimental studies and in applications in the technological sectors due to their good applicability. This kind of steel is a low-carbon martensitic and the high strength and flexibility of maraging steels make it an ideal material for applications in various industrial sectors from high pressure vessels operating in critical processes, aeronautical components, submarine hulls to sports equipment [1]. Maraging steels possess also good magnetic properties and they can be used in ultra-high speed rotors for electric hysteresis motors once maraging steels are soft magnetic materials. For this purpose, the coercive force H_c must be low [1,2] and the saturation and residual induction must be high in fields with values in the range of 20–60 A/cm and the squareness ratio must be at least 0.7 [3].

Maraging steels present a soft and deformable martensitic structure when solution annealed due to the low carbon and high nickel content in the martensitic matrix [4]. Increasing the solution annealing temperature, grains will grow. This can affect the mechanical and magnetic properties [5,6].

In the aging condition (400 °C – 650 °C), Maraging steels are hardenable and this effect can be attributed to the precipitation of some intermetallic compounds in the martensitic matrix, mainly $Ni_3(Mo, Ti)$ and Fe_2Mo [7,8]. When the only requirement is the high strength, the alloy is aged in the temperature range of 450 °C to 550 °C, but when the magnetic properties are taken into account, the alloy is aged in the temperature range of 550 °C to 650 °C [9]. During aging of maraging steels, the formation of austenite can occur as the Ni_3Ti and Fe_2Mo dissolve partially in the matrix and depending on their nickel content, the austenite formed at high aging temperatures can be retained at room temperature [10].

The microstructure and intermetallic phases can also influence the magnetic properties of maraging steels. Aging heat treatments between 500 °C and 700 °C can promote reverted austenite by diffusion controlled decomposition of martensite [11]. The composition of the maraging steels can also contribute in their magnetic properties [12–14].

Vibrating-sample magnetometer (VSM) and Magnetic Barkhausen Noise (MBN) are two important techniques to study magnetic properties of steels. The advantage of these techniques is that they are nondestructive and economical techniques and can be easily used in samples of various sizes (in case of MBN) under several external conditions. They are also sensitive to several parameters which affect the domain configuration as grain size, composition, surface conditions, hardness, residual stress and magnetic field strength.

In this research, magnetic properties of two Co-containing 18Ni 300 maraging steels were evaluated as a function of the grain size. In order to vary the grain size, four solution annealing temperature were chosen: 840, 950, 1050 and 1150 °C. The samples were solution treated for 1 h. Two aging conditions were also selected: 480 °C/3h and 560 °C/1h. The MBN and hysteresis loop in two maraging steels (300 and 350) were analyzed and discussion of the results took into account the grain size variation and a possible formation of austenite during aging [10].

2 DEVELOPMENT

2.1 Materials

The material used was the commercial Co-containing 18Ni maraging 350 steel. Its chemical composition is presented in table 1.

Alloys	Ni	Co	Mo	Ti	Al	Fe
350	17.65	11.65	4.69	1.44	0.065	Bal.

Table 1. Chemical composition (wt%) of the maraging 350 steel.

The as received condition of this material was a solution treatment at 820 °C for 1 h. The material had a disc shape with 14.00 cm in diameter and 1.28 cm in thickness.

2.2 Heat treatments

Four solution annealing temperature (840 °C, 950 °C, 1050 °C and 1150 °C) were selected in order to obtain samples with different grain sizes. The solution annealing heat treatments were carried out for 1 h in a muffle furnace followed by an air cooled to room temperature. After the solution treatment, the samples were divided in two groups: one for the aging treatment at 480 °C for 3 h and the other at 560 °C for 1 h. After aging, the samples were air cooled. The dimensions of the samples were in average 1.5 cm × 1.0 cm × 1.5 mm.

2.3 XRD characterization

For the samples of the second group (aged at 560 °C for 1 h), X-ray diffraction (XRD) measurements were carried out in order to detect any reverted austenite. The samples were sanded up to 400 mesh (SiC paper). The measurements were carried out using a Philips® X'Pert Pro diffractometer with a radiation of CoK α (0.1789 nm). The 2 θ angle ranged from 45° to 104°. XRD was not carried out for the first group of samples. According to Santos et al, aging at 480 °C up to 50 h does not form reverted austenite [15].

2.4 Growth of grain size

After the heat treatments (solution annealing followed by aging), the samples were sanded using SiC paper up to 2500 mesh, washed in distilled water and blow dried followed by polishing using alumina (Al₂O₃) of 1 and 0.05 μ m to achieve optical quality of the images after etching. In order to reveal the prior austenite grain, an electrolytic etching of 10 V with stepped time in an aqueous solution of 20% chromic acid (H₂CrO₄) was used. An Optical Microscopy (MO) using a Zeiss Microscope model Axio Imager M2m was used to obtain the images of prior austenite grains. The grain sizes were computed using the software ImageJ following the recommendations of the ASTM E112-96 [16]. In order to reveal the martensitic structure of the steels, a chemical etching with HNO₃ (4%) in methanol was used.

The samples were immersed in this reagent up to 10 s and the images were obtained by a Philips® XL-30 Scanning Electron Microscopy (SEM).

2.6 Vibrating Sample Magnetometer (VSM)

In order to measure the magnetic properties (magnetic remanence, magnetic saturation and coercive force) of the studied alloy, the VSM technique was used. The samples heat treated in all solution conditions combined with the two aging conditions were used for this test. Disks of 3.00 mm diameter and thickness in the range of 0.05 e 3.00 mm were manufactured. The measurements were carried out using an EGG-PAR model 4500 vibrating sample magnetometer (VSM). Measurements were performed at room temperature with maximum applied field of 5 kOe (400 kA/s), with 1 ms time constant and a total measurement time of 30 min. After obtaining the hysteresis graphs, the curves were corrected for demagnetization fields using the equations suggested by Chikazumi et al [17].

2.7 Magnetic Barkhausen Noise (MBN)

Magnetic Barkhausen Noise was measured on the samples for all aging treatment conditions. The sample sizes were 0.98 mm x 0.87 mm x 0.20 mm. The samples were sanded up to 220 mesh. Then they were sprinkled with alcohol and dried with a drier. The control of the excitation and processing variables and the acquisition of MBN signals were performed by the BarkTech module, developed entirely in the Dynamics and Instrumentation Laboratory of the Department of Mechanical Engineering of POLIUSP (Ladin-PME-EPUSP). The MBN measurements were carried out using a probe composed of an electromagnetic yoke which produces an alternating magnetic field on the sample, and also a coil to detect the MBN signal. The coil response is proportional to a time-variable field B that is produced using an alternating field H with frequency f. The change generated in the magnetization induces electrical impulses in the coil. MBN is isolated using amplification and the use of band pass filters. The results of these measurements were expressed as RMS (Root Mean Square) and represent the square root of the MBN signals over time. The frequency of sampling was 350 kHz, the Number of measurements on each sample was 35000, Frequency of excitation was 10 Hz, the Amplitude of excitation was 2 V and 11 Repetitions per sample.

2.8 Results and discussion

2.8.1 Study of the prior austenite grain size growth

Figure 1 shows the prior austenite grain sizes for the maraging 350 steel treated at several solution annealing temperatures and aged at 480 °C for 3 h. For the first two solution annealing temperature (840 °C and 950 °C), the grain size is not so different. The grains for these two samples presented sizes of 89.9 and 106.8 μm , respectively (Figure 1a and 1b). For the grains to grow, a movement of dislocations must happen [18]. Martensitic structure can also be seen inside the prior austenite grains. The precipitates like Ni₃Ti, TiC and other phases can act as barrier preventing the grain growth. The sample solution annealed at 1050 °C presented a grain size of 182.4 μm

(Figure. 1c). The last precipitate to dissolve in the matrix is TiC and this carbonate is responsible to hold the grain until the solution annealing temperature reaches the value of approximately 1100 °C. After this temperature, the grain is free to move. The sample solution annealed at 1150 °C obtained the largest grain size (374.6 µm) among the samples of the maraging 350 steel (Figure.1d). Above this temperature, only the austenite phase is presented. That is the reason for the grains of this sample reached so large values of grain size. The same behavior was found for the samples aged at 560 °C/ 1 h.

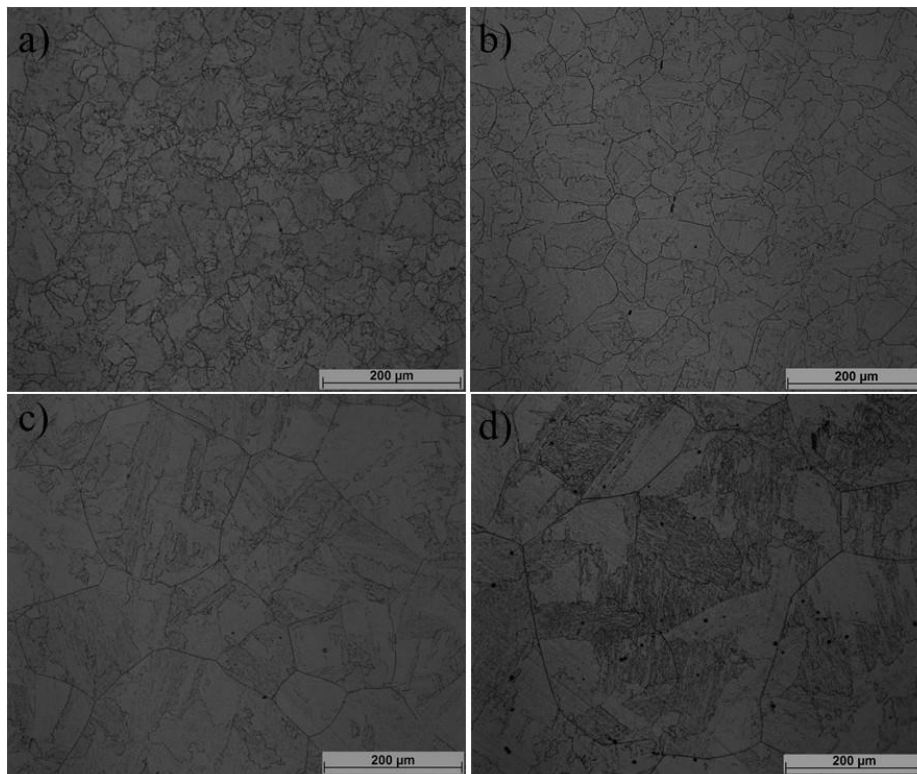


Figure 1. Optical micrograph (200 µm) Of grain size for the samples solution treated at a) 840 °C, b) 950 °C, c) 1050 °C and d) 1150 °C for 1 h. All of them aged at 480 °C/3 h.

The grain growth is exponential and the aging does not influence on the grain size as can be seen in Figure 2. For the first two grain sizes, the changing is not so considerable. After 1000 °C, the grains increase considerably reaching the maximum size for this research at 1150 °C. Martensitic blocks and laths can be seen in Figure 3. This structure was revealed after etching the surface of the samples with HNO₃ (4%) in methanol.

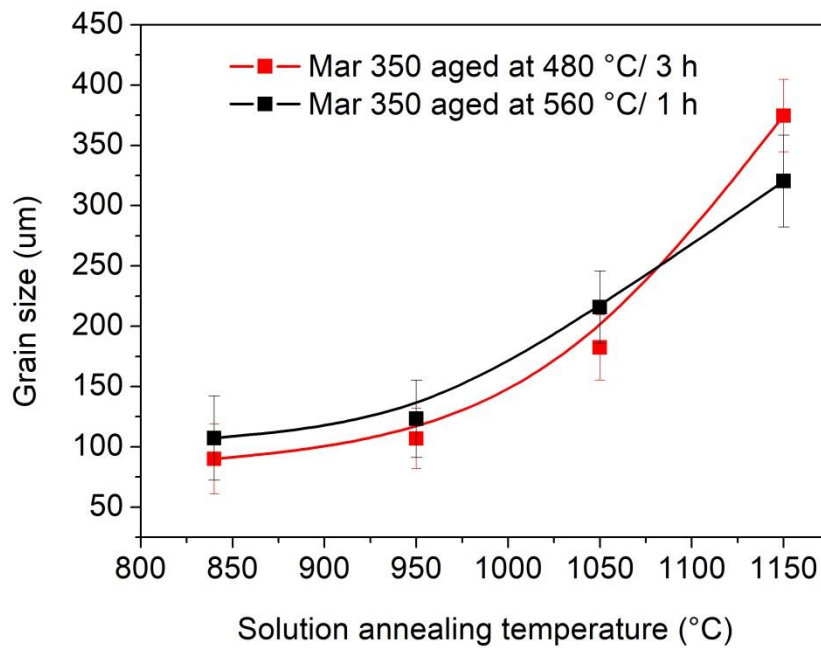


Figure 2. Grain size as a function of solution temperature for the two aging conditions.

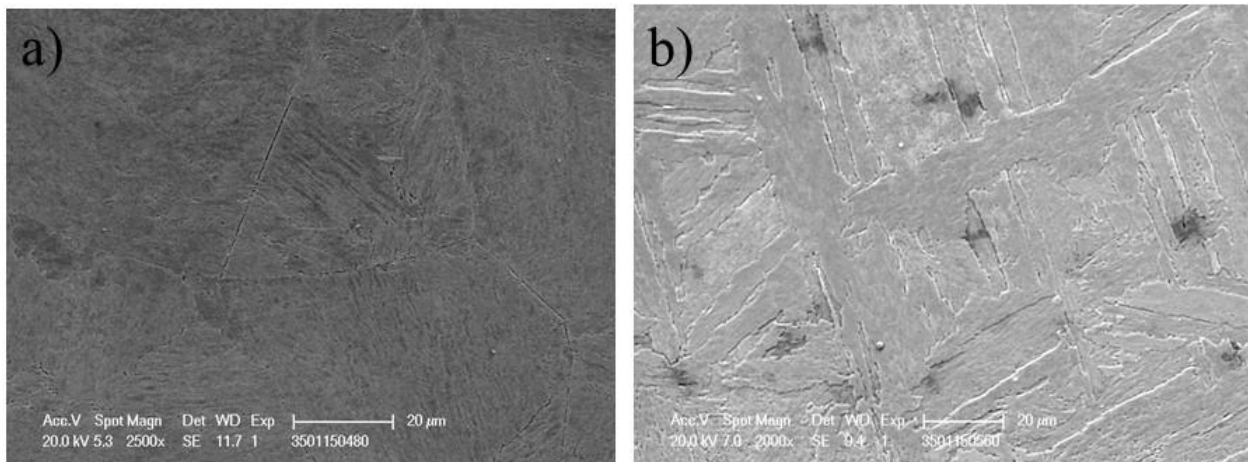


Figure 3. SEM of Martensite blocks and laths for the maraging 350 steel solution annealed at 1150 °C for 1 h and aged at a) 480 °C for 3 h and b) 560 °C for 1 h (scale of 20 µm).

2.8.2 XRD analysis

XRD measurements were performed to detect any reverted austenite on the samples solution annealed at 840 °C and 1150 °C both aged at 560 °C / 1 h (grain size extremes). Figure 4 shows the XRD patterns for these two conditions. Peaks of BBC structure were detected. These peaks correspond to the martensite phase (α'). No other peaks were detected. Aging above 500 °C for long periods of time can promote the precipitation of reverted austenite as the precipitates such as $\text{Ni}_3(\text{Ti}, \text{Mo})$ dissolve [19–21]. No diffraction peaks corresponding to reverted austenite nor the peaks of the intermetallic compounds were found meaning that the volume fractions of these phases can be below the detection limit of the technique used that is around 5 % [22]. Reverted austenite may exist for this condition but the content is too low to be detected. No reverted austenite is expected for the samples aged at 480 °C/ 3 h as reported by Santos et al [15].

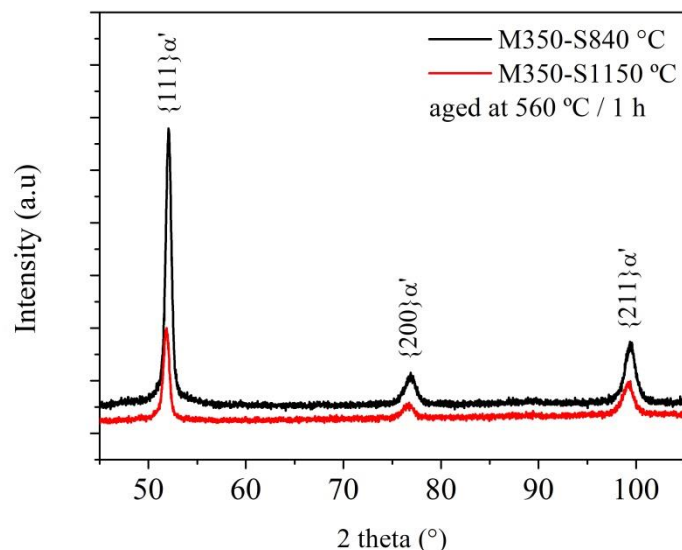


Figure 4. XRD for the samples solution annealed at extreme temperatures and aged at 560 °C for 1 h.

2.8.3 VSM analysis

One of the parameters affected with grain size was the remanence magnetization as can be seen in the graph of Figure 5a. For the smallest grain size, Maraging 350 showed the highest remanence magnetization value in the two aging conditions.

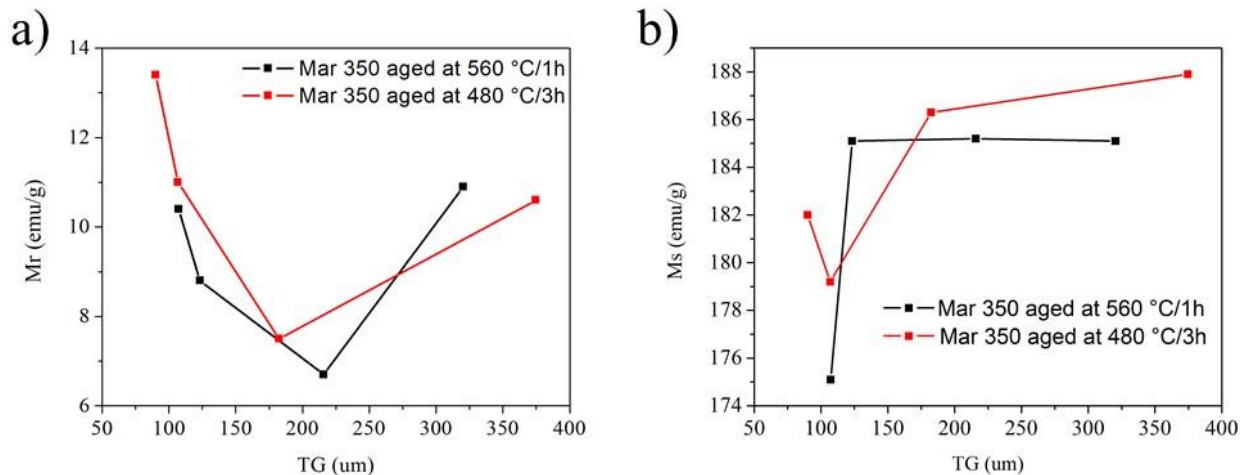


Figure 5. Remanence magnetization (a) and saturation magnetization (b) as function of grain size.

The smaller the grain size, more capacity the Maraging steel has to retain the magnetism. The remanence magnetization falls among the first three grain sizes (89.9 μm , 106.8 μm and 182.4 μm). This corresponds to the solution temperatures between 840 °C and 1050 °C. After the grain size of 182.4 μm , the remanence magnetization curve rises again for both aging conditions. Crystalline defects act as a barrier to the movement of magnetic domains. As the grain boundary is considered to be a defect in the crystalline lattice, the more grain boundaries the material possesses (the smaller the grain size), the greater the resistance to the movement of magnetic domains. On the other hand, the larger the grain, the more magnetic domains will be inside the grain, indicating that the material will also retain a little more magnetization as can be observed for the larger grain sizes in both aging conditions. This also explains why the saturation magnetization is higher for the larger grains (Figure 5b). More domains inside the grains require more magnetization to reach the saturation.

The variation of the coercive force with grain size is shown in Figure 6 for both aging conditions. The considerable variation of the coercive force is noticed when the two aging conditions are compared. The samples aged at 560 °C/1 h presented higher values for the coercive force for all the grain sizes when compared with the other aging condition (480 °C/3 h). Magnetic hardening increases as the aging temperature increases. Maraging steel is a soft magnetic material and its magnetic hardening is a disadvantage in its application. These results are in agreement with the results of Tavares et al [1] for the maraging 350. The authors studied the same magnetic properties for a larger range of aging temperatures and drew the same conclusions.

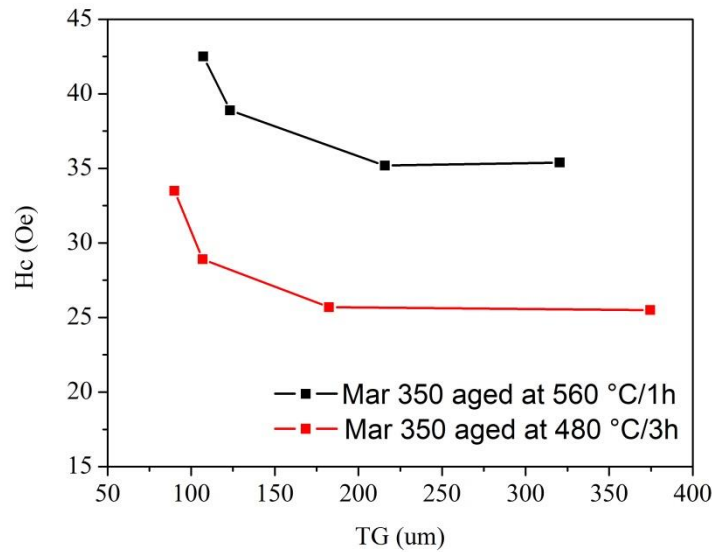


Figure 6. Coercive force for the two aging conditions in Maraging 350.

The MBN is shown in Figure 7. No significant relationship between the MBN and the grain size can be confirmed but the influence of aging condition can be noticed on the graphs. The samples aged at 560 °C for 1 h presented the lowest values for the MBN. This can be attributed to any non-magnetic phase precipitated for this aging condition, once that the MBN signal decreased when compared with the other aging condition. The exception is for the sample solution annealed at 950 °C and aged at 480 °C/3h. The decrease of MBN for this condition is not clear yet. Maybe not only the grain sizes are influencing the MBN but also the precipitates. Although not shown in the XRD diffractogram (Figure 4), this can be an indicative of the precipitation of a non-magnetic phase as reverted austenite for the aging condition of 560 °C/1 h. For this condition, its content can be less than 5 % and the XRD does not detect its peak, but MBN can detect any non-magnetic phase when the signal is measured.

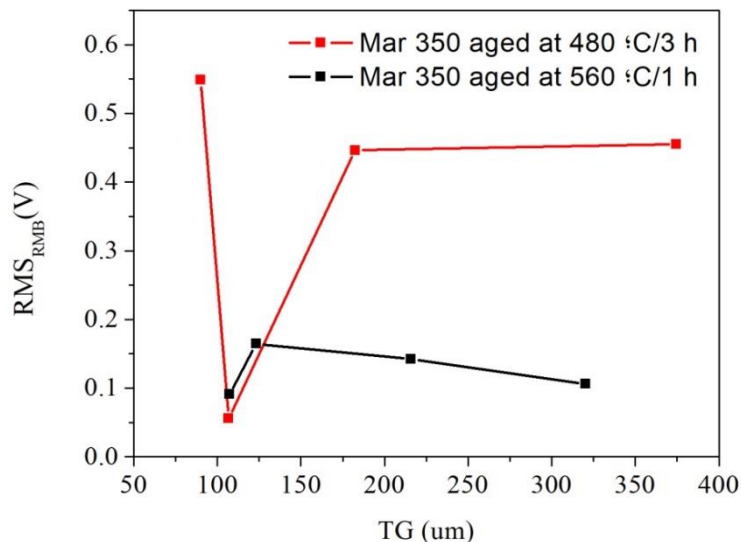


Figure 7. MBN for the maraging 350 aged at 480 °C for 3 h and 560 °C for 1 h.

Future works in this field can confirm the effect of the precipitates on the MBN considering the variation of grain size for Maraging steels.

5 CONCLUSION

The grain growth of the maraging 350 is exponential. After the solution temperature of 1050 °C, the grain increases considerably. Aging after the solution annealing treatments does not affect the grain size. Magnetic properties as remanence and saturation magnetization are also influenced by the grain size once that these properties presented a similar behavior for the two aging conditions showed in the graphs. As the aging temperature increases, the coercive force also increases indicating a magnetic hardening of the material. The aging conditions affect also the MBN, indicating a possible non-magnetic phase precipitated along the microstructure.

Acknowledgments

The authors would like to thank to CAPES for the financial support and also to the Federal Fluminense Univeristy where the Barkhausen measurements were carried out.

REFERENCES

- 1 S.S.M. Tavares, M.R. Da Silva, J.M. Neto, J.M. Pardal, M.P.C. Fonseca, H.F.G. Abreu, Magnetic properties of a Ni–Co–Mo–Ti maraging 350 steel, *J. Alloys Compd.* 373 (2004) 304–311.
- 2 M. Ahmed, A. Ali, S.K. Hasnain, F.H. Hashmi, A.Q. Khan, Magnetic properties of maraging steel in relation to deformation and structural phase transformations, *Acta Metall. Mater.* 42 (1994) 631–638.
- 3 R. Tewari, S. Mazumder, I.S. Batra, G.K. Dey, S. Banerjee, Precipitation in 18 wt% Ni maraging steel of grade 350, *Acta Mater.* 48 (2000) 1187–1200. doi:10.1016/S1359-6454(99)00370-5.
- 4 J.M. Pardal, S.S.M. Tavares, M.P.C. Fonseca, M.R. da Silva, J.M. Neto, H.F.G. Abreu, Influence of temperature and aging time on hardness and magnetic properties of the maraging steel grade 300, *J. Mater. Sci.* 42 (2007) 2276–2281.
- 5 J. Anglada-Rivera, L.R. Padovese, J. Capo-Sanchez, Magnetic Barkhausen noise and hysteresis loop in commercial carbon steel: influence of applied tensile stress and grain size, *J. Magn. Magn. Mater.* 231 (2001) 299–306.
- 6 R. Ranjan, D.C. Jiles, O. Buck, R.B. Thompson, Grain size measurement using magnetic and acoustic Barkhausen noise, *J. Appl. Phys.* 61 (1987) 3199–3201.
- 7 R. Tewari, S. Mazumder, I.S. Batra, G.K. Dey, S. Banerjee, Precipitation in 18 wt% Ni maraging steel of grade 350, *Acta Mater.* 48 (2000) 1187–1200. doi:10.1016/S1359-6454(99)00370-5.
- 8 J.B. Lecomte, C. Servant, G. Cizeron, A comparison of the structural evolution occurring during anisothermal or isothermal treatments in the case of nickel and manganese type maraging alloys, *J. Mater. Sci.* 20 (1985) 3339–3352.
- 9 M. Ahmed, K. Hasnain, I. Nasim, H. Ayub, Magnetic properties of maraging steels in relation to nickel concentration, *Metall. Mater. Trans. A.* 26 (1995)

- 1869–1876.
- 10 X. Li, Z. Yin, Reverted austenite during aging in 18Ni(350) maraging steel, *Mater. Lett.* 24 (1995) 239–242. doi:10.1016/0167-577X(95)00109-3.
 - 11 F. Habiby, A. Ul Haq, A.Q. Khan, Influence of austenite on the coercive force, electrical resistivity and hardness of 18% Ni maraging steels, *Mater. Des.* 13 (1992) 259–264.
 - 12 M. Blaow, J.T. Evans, B.A. Shaw, Effect of hardness and composition gradients on Barkhausen emission in case hardened steel, *J. Magn. Magn. Mater.* 303 (2006) 153–159.
 - 13 J. Kameda, R. Ranjan, Nondestructive evaluation of steels using acoustic and magnetic Barkhausen signals—I. Effect of carbide precipitation and hardness, *Acta Metall.* 35 (1987) 1515–1526.
 - 14 M. Blaow, J.T. Evans, B.A. Shaw, The effect of microstructure and applied stress on magnetic Barkhausen emission in induction hardened steel, *J. Mater. Sci.* 42 (2007) 4364–4371.
 - 15 L.P.M. Santos, M. Béreš, I.N. Bastos, S.S.M. Tavares, H.F.G. Abreu, M.J. Gomes da Silva, Hydrogen embrittlement of ultra high strength 300 grade maraging steel, *Corros. Sci.* 101 (2015) 12–18. doi:10.1016/j.corosci.2015.06.022.
 - 16 P. American Society for Testing and Materials (Filadelfia, ASTM E112-96 (2004) e2: Standard Test Methods for Determining Average Grain Size, in: ASTM, 2004.
 - 17 S. Chikazumi, C.D. Graham, *Physics of Ferromagnetism 2e*, Oxford University Press on Demand, 2009.
 - 18 F. Wakai, M. Yoshida, Y. Shinoda, T. Akatsu, Coarsening and grain growth in sintering of two particles of different sizes, *Acta Mater.* 53 (2005) 1361–1371.
 - 19 W. Sha, A. Cerezo, G.D.W. Smith, Phase Chemistry and Precipitation Reactions in Maraging Steels: Part IV. Discussion and Conclusions, *Metall. Trans. A.* 24 (1993) 1221–1232.
 - 20 U.K. Viswanathan, G.K. Dey, V. Sethumadhavan, Effects of austenite reversion during overageing on the mechanical properties of 18 Ni (350) maraging steel, *Mater. Sci. Eng. A.* 398 (2005) 367–372. doi:10.1016/j.msea.2005.03.074.
 - 21 U.K. Viswanathan, G.K. Dey, M.K. Asundi, Precipitation hardening in 350 grade maraging steel, *Metall. Trans. A.* 24 (1993) 2429–2442. doi:10.1007/BF02646522.
 - 22 B.. Cullity, *Elements of Diffraction*, 2nd editio, Addison-Wesley Publishing Company, Inc., 1978.